

Timber species range



Accoya



Alaskan Yellow Cedar



American Black Walnut
(veneer) FR MDF



Ash (UK), (EU) & (US)




Bamboo (dark)




Bamboo (light)



Bamboo (medium)

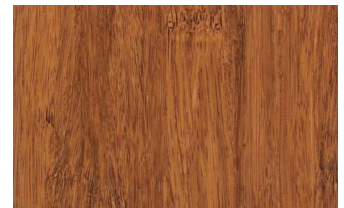

Bamboo (strand woven)

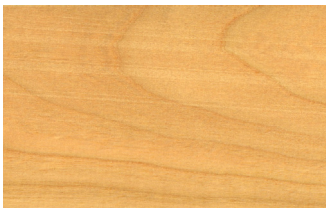

Cherry (US)




Douglas Fir



Dragon Wood
(charred effect)



European Redwood

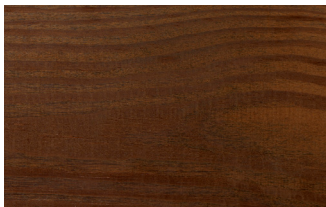


Kebony (dark Thermo-
modified Pine)




Larch (EU)




Oak (solid), Oak (veneer) FR
MDF & American White Oak

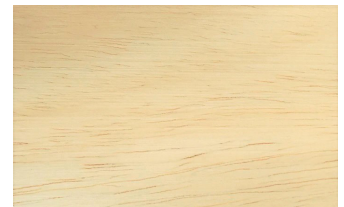

Obeche / Ayous

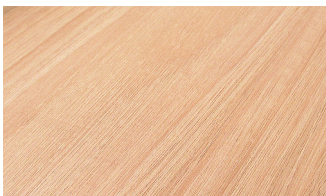

Red Grandis

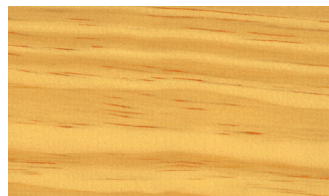

Southern Yellow Pine




Sweet Chestnut



Thermo Ash (UK)



Thermo Euro-Pine

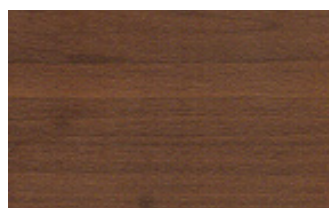

Thermo Poplar (UK)



Western Red Cedar



Yellow Poplar

Timber species range



Species Name	Source	Certification	External Use	Density (Kg/ m3)	Janka Hardness (lbs)	Durability	Movement Risk
Accoya	New Zealand	FSC	Yes	450	550	High	Low
Alaskan Yellow Cedar	USA	PEFC	Yes	450	400	High	Low
American Black Walnut (veneer) FR MDF	China or EU	FSC	No	700	1100	Low	Low
American White Oak	USA	FSC	No	670	1360	Medium	Medium
Ash (EU)	Europe	FSC	No	675	1320	Low	Medium
Ash (UK)	UK	GiB	No	675	1320	Low	Medium
Ash (US)	USA	FSC	No	675	1320	Low	Medium
Bamboo (dark)	China	FSC	No	700	1200	Low	Low
Bamboo (light)	China	FSC	No	700	1200	Low	Low
Bamboo (medium)	China	FSC	No	700	1200	Low	Low
Bamboo (strand woven)	China	FSC	Yes	1200	3500	High	Low
Cherry (US)	USA	PEFC	No	625	950	Medium	Low
Douglas Fir	USA	PEFC	Yes	530	660	Medium	Low
DragonWood (charred effect)	Europe	FSC	Yes	510	420	High	Low
European Redwood	Europe	FSC	No	520	420	Low	Low
Kebony (dark Thermo-modified Pine)	USA	FSC	Yes	700	1600	High	Low
Larch (Eu)	Europe	FSC	Yes	600	745	High	Medium
Oak (solid)	Europe	FSC	Yes	725	1050	High	Medium
Oak (veneer) FR MDF	China or EU	FSC	No	700	1100	Low	Low
Obeche / Ayous	Africa	FSC	No	390	430	Low	Low
Red Grandis	South America	FSC	Yes	550	720	High	Low
Southern Yellow Pine	USA	PEFC	No	660	750	Medium	Low
Sweet Chestnut	Europe	PEFC	Yes	575	540	High	Medium
Thermo Ash (UK)	UK	GiB	Yes	590	1100	High	Low
Thermo Euro-Pine	Europe	FSC	Yes	450	500	High	Low
Thermo Poplar (UK)	Uk	GiB	Yes	400	500	High	Low
Western Red Cedar	Canada	PEFC	Yes	390	350	High	Low
Yellow Poplar	USA	FSC	No	450	540	Low	Low